



# A biferrocenium salt containing paramagnetic tetracyanoquinodimethane hexamers: charge disproportionation via donor-acceptor interactions

Mochida, Tomoyuki ; Funasako, Yusuke ; Takahashi, Kazuyuki ; Inokuchi, Makoto ; Sakurai, Takahiro ; Ikeda, Shohei ; Ohta, Hitoshi ; Mori, ...

---

(Citation)

Chemical Communications, 50(87):13370-13372

(Issue Date)

2014-09-11

(Resource Type)

journal article

(Version)

Accepted Manuscript

(URL)

<https://hdl.handle.net/20.500.14094/90002756>



## COMMUNICATION

# A biferrocenium salt containing paramagnetic tetracyanoquinodimethane hexamers: Charge disproportionation via donor–acceptor interactions†

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Tomoyuki Mochida,<sup>\*a</sup> Yusuke Funasako,<sup>a,b</sup> Kazuyuki Takahashi,<sup>a</sup> Makoto Inokuchi,<sup>b</sup> Takahiro Sakurai,<sup>c</sup> Shohei Ikeda,<sup>d</sup> Hitoshi Ohta,<sup>e</sup> Hatsumi Mori<sup>f</sup> and Mikio Uruichi<sup>g</sup>

**[Dineopentyl-biferrocene]<sub>2</sub>[Cl<sub>1</sub>TCNQ]<sub>7</sub>**, which has an unprecedented high donor–acceptor ratio of 2:7, contains a linear paramagnetic hexamer of Cl<sub>1</sub>TCNQ. Both the donor and acceptor molecules exhibit charge disproportionation in the crystal through mutual electrostatic interactions.

Crystal engineering of mixed valence compounds has been a topic of continuous interest for many years. Biferrocene is an electron donor (D) comprised of two ferrocene units exhibiting both mixed-valence monocation (D<sup>+</sup>) and non-mixed-valence dication (D<sup>2+</sup>) oxidation states. To date, many biferrocenium salts containing D<sup>+</sup> have been prepared, and their valence states have been extensively investigated.<sup>1</sup> Recently, we prepared a series of alkyl-biferrocenium salts with various acceptor (A) molecules, including tetracyanoquinodimethane (TCNQ) derivatives.<sup>2,3</sup> Salts with a D/A ratios of 1:1–1:3 were obtained; the valency of the donor changes from D<sup>+</sup> to D<sup>2+</sup> with increasing stoichiometry. In particular, the intermediate salts contain both D<sup>2+</sup> and D<sup>+</sup> molecules.<sup>2a,b</sup> The coexistence of dications and monocations is an interesting phenomenon that has also been found in viologen salts.<sup>4</sup> Charge disproportionation, or charge separation, is an important topic in the physics of charge-transfer salts.

This communication reports the structure and valence state of a biferrocenium salt, i.e., [dineopentyl-biferrocene]<sub>2</sub>[Cl<sub>1</sub>TCNQ]<sub>7</sub> **1** (Fig. 1), with a D/A ratio of 2:7,<sup>5</sup> which is the highest ratio to date among reported biferrocenium salts. We reported previously that [dineopentyl-biferrocene][F<sub>1</sub>TCNQ]<sub>3</sub> exhibits a charge-transfer phase transition between the monovalent state ([D]<sup>+</sup>[A<sub>3</sub>]<sup>−</sup>) and divalent state ([D]<sup>2+</sup>[A<sub>3</sub>]<sup>2−</sup>) at around 120 K. The transition can be controlled by molecular modification while maintaining the crystal structure.<sup>3</sup> However, the use of Cl<sub>1</sub>TCNQ, which has comparable electron affinity but slightly larger molecular volume than F<sub>1</sub>TCNQ, afforded the salt of **1** with a different D/A ratio and structure. As described below, both the donor and acceptor units exhibit charge disproportionation in this salt, the valence state of which is represented as [D]<sup>2+</sup>[D]<sup>+</sup>[A<sub>6</sub>]<sup>3−</sup>[A]<sup>0</sup>. Interestingly, this salt contains a paramagnetic hexamer of the acceptor.


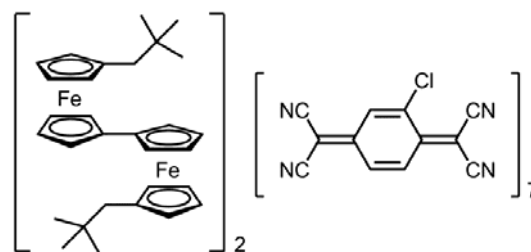


Fig. 1. Structural formula of [dineopentyl-biferrocene]<sub>2</sub>[Cl<sub>1</sub>TCNQ]<sub>7</sub> **1**.

X-Ray crystallography revealed that this salt has a segregated-stack structure, where the donor and acceptor each form a columnar stack along the [1 0 −2] direction (Fig. 2a, Fig. S1, ESI†).<sup>6</sup> Two crystallographically independent donor molecules, D<sup>2+</sup> and D<sup>+</sup>, exist in the crystal, as determined from the differing bond lengths.<sup>2,7</sup> Both are located on inversion centers, and the valence in the latter molecule is averaged owing to rapid electron transfer between Fe<sup>3+</sup> and Fe<sup>2+</sup>. This charge disproportionation is ascribed to the difference in local electrostatic interactions between the donors and acceptors, similar to previously reported salts containing D<sup>2+</sup> and D<sup>+</sup>.<sup>2a</sup> The molecular arrangement viewed along the stacking direction is shown in Fig. 2b. Each Fe atom in the D<sup>2+</sup> state is surrounded by three electronegative cyano groups from the acceptors (CN⋯Fe distances: 4.098, 4.128, and 4.260 Å), which stabilizes the dication state. Such CN⋯Fe proximity often dominates the valence state in biferrocenium salts.<sup>2</sup> In contrast, the Fe atoms in the D<sup>+</sup> state have only one nearby cyano group at a longer CN⋯Fe distance of 4.326 Å.

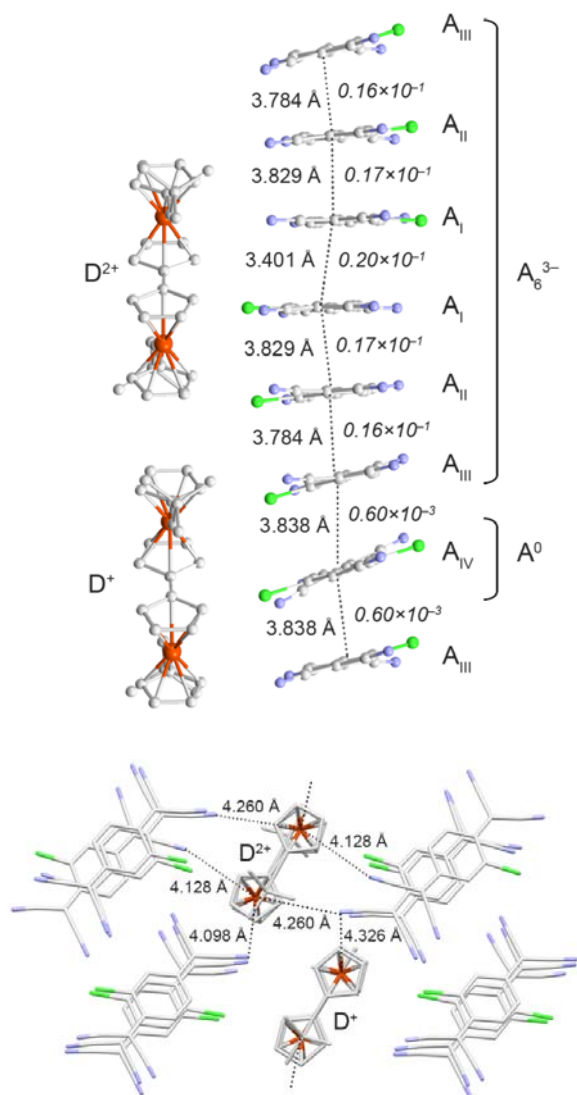


**Fig. 2.** Molecular arrangement of **1** viewed a) perpendicular to the stacking direction, where intermolecular centroid-centroid distances are indicated by dashed lines and the values of the overlap integrals are shown in italics, and b) along the stacking direction, where short CN...Fe intermolecular distances are indicated by dotted lines.

The acceptor molecules also exhibit charge disproportionation. In the acceptor column, four crystallographically independent molecules (A<sub>I</sub>–A<sub>IV</sub>) are present, of which A<sub>I</sub>–A<sub>III</sub> have negative charges of –0.5 and A<sub>IV</sub> is neutral.<sup>9</sup> A<sub>I</sub>–A<sub>III</sub> form a linear centrosymmetric hexamer, i.e., [A<sub>III</sub>–A<sub>II</sub>–A<sub>I</sub>–A<sub>I</sub>–A<sub>II</sub>–A<sub>III</sub>]<sup>3-</sup>, that accommodates three electrons (**Fig. 2a**). The neutral molecule, A<sub>IV</sub>, is located between the hexamers and is more tilted with respect to the stacking axis than A<sub>I</sub>–A<sub>III</sub>. The intermolecular overlap integrals calculated using the EHMO method<sup>10</sup> were comparable in the hexamer (16–20×10<sup>-3</sup>, shown in **Fig. 2a**), although the interplane distances in the unit exhibited some variation (centroid-centroid: 3.40–3.83 Å, centroid-plane: 3.26–3.30 Å). The overlap integrals between the neutral and adjacent molecules were much smaller (0.6×10<sup>-3</sup>); therefore, the hexamer can be regarded as an electronically isolated uniform unit. The charge disproportionation in the crystal is again accounted for by intermolecular electrostatic interactions: A<sub>I</sub>–A<sub>III</sub> have short

CN...Fe distances with cations via one or two cyano groups, while A<sub>IV</sub> has no such interaction. Furthermore, the negatively charged hexamer is adjacent to D<sup>2+</sup>, while A<sub>IV</sub> is adjacent to D<sup>+</sup> (**Fig. 2**).

The valence state of **1** was further investigated by magnetic susceptibility measurements (**Fig. 3**). The  $\chi T$  value was 2.16 emu K mol<sup>-1</sup> at room temperature and nearly temperature independent down to ~20 K, below which the value sharply decreased. As the hexamer accommodates three electrons in delocalized molecular orbitals, one unpaired spin should remain. The magnetic moments of the organic radical and ferrocenium cation are 0.375 and ~0.6 emu K mol<sup>-1</sup>, respectively.<sup>2</sup> The observed susceptibility is in excellent agreement with one spin on the hexamer and three spins on the Fe atoms, of which two are from D<sup>2+</sup> and one is from D<sup>+</sup> (0.375 + 0.6 × 3 = 2.175 emu K mol<sup>-1</sup>). The temperature independent behavior indicates that the magnetic interaction between the hexamers is small. In the ESR spectrum, a very broad isotropic signal was observed at room temperature ( $g = 2.01$ ,  $\Delta H_{p-p} = 300$  G; **Fig. S2a**, ESI†), which is ascribed to the spin delocalized on the hexamer. Signals from the cation spins were unobserved at room temperature because of the fast relaxation, whereas a typical anisotropic signal<sup>11</sup> of the cation spin ( $g_{||} = 3.40$ ,  $g_{\perp} = 2.00$ ) appeared at 77 K (**Fig. S2b**, ESI†). The temperature dependence of the ESR spectra of the single crystals, which displayed separate signals of the cation spin and anion spin, is consistent with this feature (**Fig. S3**, ESI†).

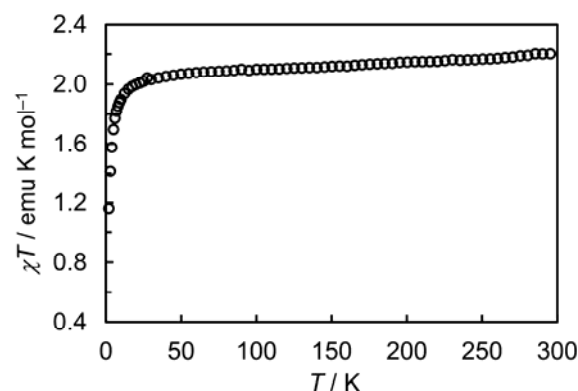

**Fig. 3.** Temperature dependence of the magnetic susceptibility ( $\chi T$ ) of **1**.

The hexamer unit, in which the unpaired electron is confined, is regarded as a quantum well that is ~2 nm length. Electronic excitations in the hexamer were observed as a very broad absorption peak in the infrared region around 3500 cm<sup>-1</sup> (**Fig. S4**, ESI†), similar to the very broad peak at around 3300 cm<sup>-1</sup> exhibited by (F<sub>1</sub>TCNQ)<sub>3</sub><sup>-</sup>.<sup>12</sup> The electrical conductivity along the stacking axis of the crystal is 2 × 10<sup>-2</sup> S cm<sup>-1</sup> at room temperature. This salt is a semiconductor with an activation energy of 90 meV.

In summary, a biferrocenium salt with a high D/A ratio containing an electronically isolated paramagnetic hexamer of Cl<sub>1</sub>TCNQ was synthesized. This salt is another example of a biferrocenium salt in which D<sup>2+</sup> and D<sup>+</sup> coexist in a single crystal; charge disproportionation occurs via donor-acceptor electrostatic interactions. TCNQ derivatives often form one-dimensional stacks; high D/A ratios in their salts are rare.<sup>13,14a</sup> Several salts containing pentamers<sup>14</sup> or heptamers<sup>15</sup> of TCNQ have been reported, but most of them have interunit interactions and non-magnetic ground states. The hexamer unit in this salt is a quantum well that is nanometer sized. Therefore, arrays of

quantum wells are aligned on the crystal surfaces of this salt. This feature is interesting from the perspective of electronic applications.

We thank K. Takazawa (Toho University) for his assistance with the sample preparation. This work was supported financially by KAKENHI (grant number 26104524).

<sup>a</sup>Department of Chemistry, Graduate School of Science, Kobe University, Rokkodai, Nada, Hyogo 657-8501, Japan. E-mail: tmochida@platinum.kobe-u.ac.jp; Fax: +81 78 803 5679; Tel: +81 78 803 5679.

<sup>b</sup>Department of Applied Chemistry, Faculty of Engineering, Tokyo University of Science, Yamaguchi, Onoda, Yamaguchi 756-0884, Japan

<sup>c</sup>Center for Supports to Research and Education Activities, Kobe University, Kobe, Hyogo 657-8501, Japan

<sup>d</sup>Department of Physics, Graduate School of Science, Kobe University, Kobe, Hyogo 657-8501, Japan

<sup>e</sup>Molecular Photoscience Research Center, Kobe University, Kobe, Hyogo 657-8501, Japan

<sup>f</sup>Institute for Solid State Physics, The University of Tokyo, Kashiwanoha, Kashiwa, Chiba 277-8581, Japan

<sup>g</sup>Institute for Molecular Science, Myodaiji, Okazaki, Aichi 444-8585, Japan


†Electronic supplementary information (ESI) available: Crystal structure, ESR spectra, NIR/MIR spectrum, and crystallographic data. CCDC 992524 (1). For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/

## Notes and references

- (a) D. O. Cowan, R. L. Collins and F. J. Kaufman, *Phys. Chem.*, 1971, **75**, 2025–2030; (b) D. N. Hendrickson, in *Mixed Valency Systems: Applications in Chemistry, Physics, and Biology, Series C*, ed. K. Prassides, NATO ASI Series, Kluwer, Dordrecht, 1991, vol.343, 67–90; (c) W. H. Morrison and D. N. Hendrickson, *Inorg. Chem.*, 1975, **14**, 2331–2346; (d) T.-Y. Dong, L.-S. Chang, G.-H. Lee and S.-M. Peng, *Organometallics*, 2002, **21**, 4192–4200; (e) H. Sano, *Hyperfine Interact.*, 1990, **53**, 97–112.
- (a) T. Mochida, Y. Funasako, E. Nagabuchi and H. Mori, *Cryst. Growth Des.*, 2014, **14**, 1459–1466; (b) T. Mochida, E. Nagabuchi, M. Takahashi and H. Mori, *Chem. Commun.*, 2014, **50**, 2481–2483; (c) T. Mochida, K. Takazawa, H. Matsui, M. Takahashi, M. Takeda, M. Sato, Y. Nishio, K. Kajita and H. Mori, *Inorg. Chem.*, 2005, **44**, 8628–8641; (d) T. Mochida, Y. Funasako, S. Yamazaki and H. Mori, *Eur. J. Inorg. Chem.*, 2014, **24**, 3920–3926.
- (a) T. Mochida, Y. Funasako, K. Takazawa, M. Takahashi, M. M. Matsushita and T. Sugawara, *Chem. Commun.*, 2014, **50**, 5473–5475; (b) M. Uruichi, Y. Yue, K. Yakushi and T. Mochida, *J. Phys. Soc. Jpn.*, 2007, **76**, 124707/1–6; (c) T. Mochida, K. Takazawa, M. Takahashi, M. Takeda, Y. Nishio, M. Sato, K. Kajita, H. Mori, M. M. Matsushita and T. Sugawara, *J. Phys. Soc. Jpn.*, 2005, **74**, 2214–2216.
- N. Leblanc, N. Mercier, O. Toma, A. H. Kassiba, L. Zorina, P. Auban-Senzier and C. Pasquier, *Chem. Commun.*, 2013, **49**, 10272–10274.
- A hot dichloromethane solution (3 mL) of chlorotetracyanoquinodimethane (2.8 mg,  $1.2 \times 10^{-2}$  mol) was added dropwise to a hot dichloromethane solution (1 mL) of 1',1''-dineopentyl-1,1''-biferrocene (6.0 mg,  $1.2 \times 10^{-2}$  mmol), and the solution was stirred for several minutes. Vapor diffusion of pentane into the solution at room temperature produced black elongated plate crystals. Yield: 3.7 mg (23%). Anal. Calcd for  $C_{144}H_{97}N_{28}Cl_7Fe_4$ : C, 64.27; H, 3.63; N, 14.57. Experimental: C, 64.38; H, 3.77; N, 14.01. IR (KBr,  $cm^{-1}$ ): 3433, 2181 (CN), 1561, 1528, 1328, 1244, 1169, 1034, 774, 647.
- Crystal data for **1** at 90 K: triclinic,  $P\bar{1}$ ,  $a = 10.484(5)$  Å,  $b = 16.267(7)$  Å,  $c = 19.578(9)$  Å,  $\alpha = 86.044(6)^\circ$ ,  $\beta = 79.030(6)^\circ$ ,  $\gamma = 71.980(7)^\circ$ ,  $V = 3117(2)$  Å<sup>3</sup>,  $Z = 1$ ,  $R_1 = 0.0848$ , and  $wR_2 = 0.2101$ . See ESI† for details.
- The Fe–C<sub>5</sub>H<sub>4</sub>R (centroid) distance and Fe–C<sub>5</sub>H<sub>4</sub>R average distance in D<sup>2+</sup> are 1.713 Å and 2.098 Å, respectively, which corresponds to the values for ferrocenium cation. The corresponding distances in D<sup>+</sup> are 1.686 Å and 2.079 Å, respectively, which are both intermediate values of neutral ferrocene and ferrocenium cation.<sup>2a</sup>
- T. J. Kistenmacher, T. J. Emage, A. N. Bloch, and D. O. Cowan, *Acta Crystallogr., Sect B*, 1982, **38**, 1193–1199.
- The negative charges on A<sub>I</sub>–A<sub>IV</sub> estimated from the bond lengths<sup>8</sup> are –0.44, –0.46, –0.42, and –0.06, respectively. In the Raman spectrum, the charge-sensitive C=C stretching mode was observed at 1422 cm<sup>–1</sup>, between the frequencies for monoanion (1446 cm<sup>–1</sup>; Li salt) and neutral (1396 cm<sup>–1</sup>) species.
- T. Mori, A. Kobayashi, Y. Sasaki, H. Kobayashi, G. Saito and H. Inokuchi, *Bull. Chem. Soc. Jpn.*, 1984, **57**, 627–633.
- S. Nakashima, Y. Masuda, I. Motoyama and H. Sano, *Bull. Chem. Soc. Jpn.*, 1987, **60**, 1673–1680.
- M. Uruichi, K. Yakushi and T. Mochida, *J. Low Temp. Phys.*, 2006, **142**, 655–658.
- (a) A. Graja, A. Bogucki, *Mini-Rev. Org. Chem.*, 2010, **7**, 145–160. (b) X. Qu, J. Lu, J. F. Boas, A. M. Bond and L. L. Martin, *Chem. Eur. J.*, 2011, **17**, 9350–9358.
- (a) J. Lu, X. Qu, G. Peleckis, J. F. Boas, A. M. Bond and L. L. Martin, *J. Org. Chem.*, 2011, **76**, 10078–10082; (b) G. J. Ashwell, D. D. Eley, N. J. Drew, S. C. Wallwork and M. R. Willis, *Acta Crystallogr., Sect B*, 1978, **34**, 3608–3612; (c) G. J. Ashwell, D. D. Eley, A. Harper, A. C. Torrance, S. C. Wallwork and M. R. Willis, *Acta Crystallogr., Sect B*, 1977, **33**, 2258–2263; (d) G. J. Ashwell, D. D. Eley, S. C. Wallwork, M. R. Willis, G. D. Welch and J. Woodward, *Acta Crystallogr., Sect B*, 1977, **33**, 2252–2257.
- (a) S. Zürcher, J. Petrig, V. Gramlich, M. Worle, C. Mensing, D. von Arx and A. Togni, *Organometallics*, 1999, **18**, 3679–3689; (b) M. Konno and Y. Saito, *Acta Crystallogr., Sect B*, 1981, **37**, 2034–2043.

**Table of contents entry**

[Dineopentyl-biferrocene]<sub>2</sub>[Cl<sub>1</sub>TCNQ]<sub>7</sub>, which has a high donor–acceptor ratio of 2:7, contains a linear paramagnetic hexamer of Cl<sub>1</sub>TCNQ.

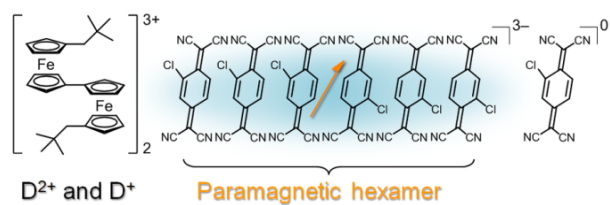

## Electronic Supplementary Information

## A biferrocenium salt containing paramagnetic tetracyanoquinodimethane hexamers: Charge disproportionation via donor–acceptor interactions

Tomoyuki Mochida,<sup>a,\*</sup> Yusuke Funasako,<sup>a,b</sup> Kazuyuki Takahashi,<sup>a</sup> Makoto Inokuchi,<sup>b</sup> Takahiro Sakurai,<sup>c</sup> Shohei Ikeda,<sup>d</sup> Hitoshi Ohta,<sup>e</sup> Hatsumi Mori<sup>f</sup> and Mikio Uruichi<sup>g</sup>

<sup>a</sup>Department of Chemistry, Graduate School of Science, Kobe University, Rokkodai, Nada, Hyogo 657-8501, Japan. E-mail: tmochida@platinum.kobe-u.ac.jp; Fax: +81 78 803 5679; Tel: +81 78 803 5679

<sup>b</sup>Department of Applied Chemistry, Faculty of Engineering, Tokyo University of Science, Yamaguchi, Sanyoonoda, Yamaguchi 756-0884, Japan


<sup>c</sup>Center for Supports to Research and Education Activities, Kobe University, Kobe, Hyogo 657-8501, Japan

<sup>d</sup>Department of Physics, Graduate School of Science, Kobe University, Kobe, Hyogo 657-8501, Japan


<sup>e</sup>Molecular Photoscience Research Center, Kobe University, Kobe, Hyogo 657-8501, Japan

<sup>f</sup>Institute for Solid State Physics, The University of Tokyo, Kashiwanoha, Kashiwa, Chiba 277-8581, Japan


<sup>g</sup>Institute for Molecular Science, Myodaiji, Okazaki, Aichi 444-8585, Japan

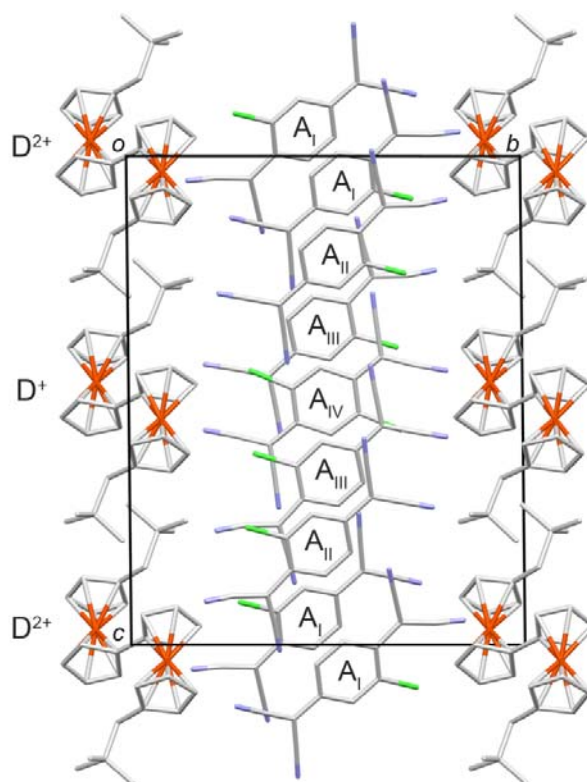


**Fig. S1.** Packing diagram of [dineopentyl-biferrocene]<sub>2</sub>[Cl<sub>1</sub>TCNQ]<sub>7</sub> (**1**) viewed along the *a*-axis.

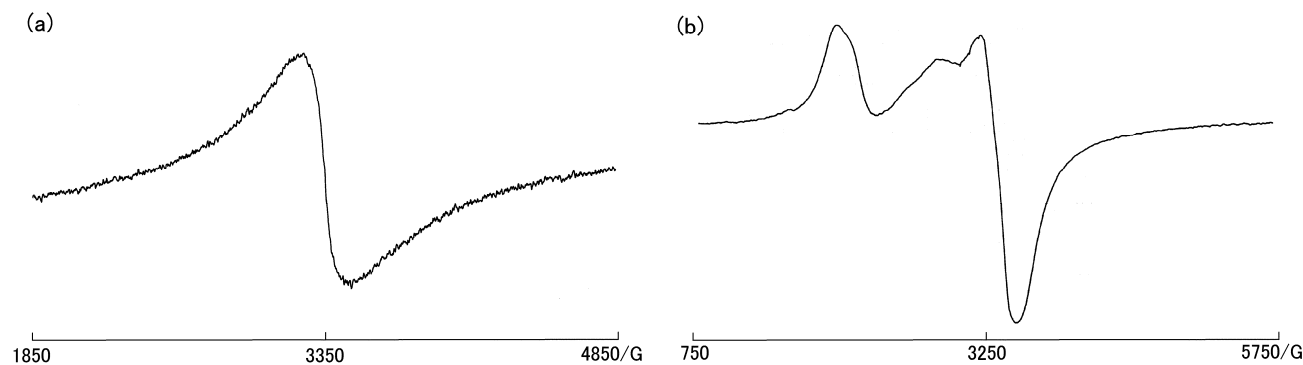

**Fig. S2.** ESR spectra of polycrystalline samples of **1** recorded at (a) room temperature and (b) 77 K.

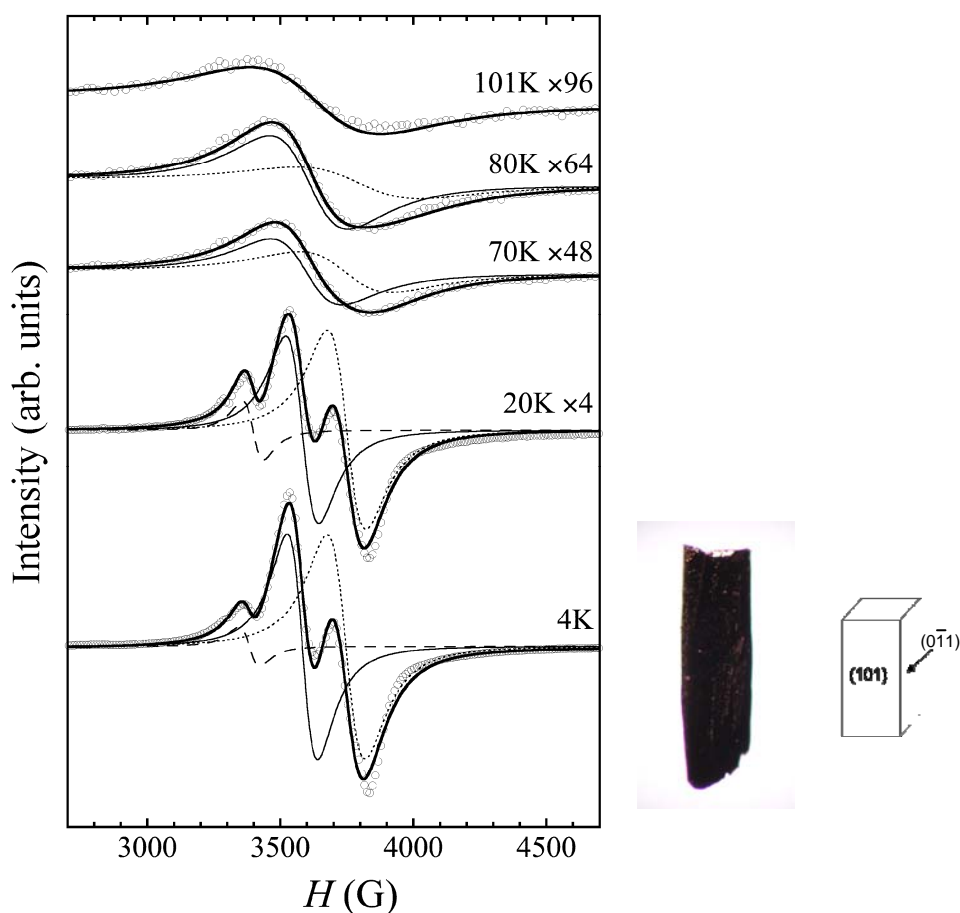

**Fig. S3.** Temperature dependence of the ESR spectra of oriented crystals of **1** recorded under magnetic fields applied normal to the (101) plane. The data points and fitting curves are indicated by circles ( $\circ$ ) and bold lines, respectively. Fitting was done via summation of the TCNQ component (thin line), ferrocenium component (dotted line), and impurity (dashed line). A photograph of a plate-like single crystal of **1** (~0.3 mm length) is shown on the right.

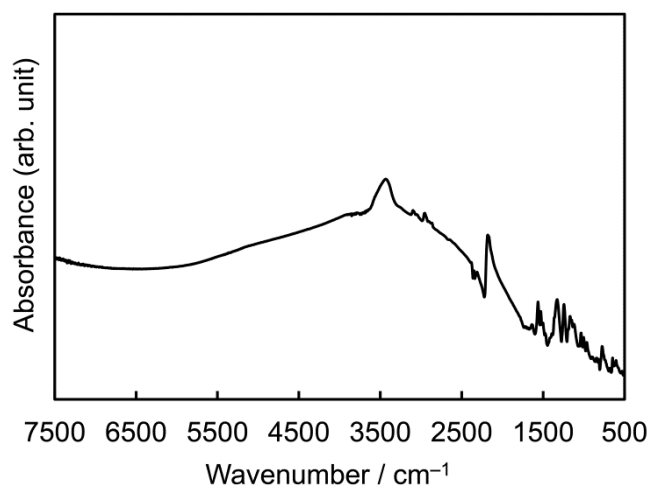

**Fig. S4.** Absorption spectrum of **1** in the NIR-IR region at room temperature (KBr pellet).